

9-2004

Comment on "Self-Organized Periodic Photonic Structure in a Nonchiral Liquid Crystal"

Oleg P. Pishnyak

Kent State University - Kent Campus, opp@lci.kent.edu

Yuriy A. Nastishin

Kent State University - Kent Campus

Oleg Lavrentovich

Kent State University - Kent Campus, olavrent@kent.edu

Follow this and additional works at: <http://digitalcommons.kent.edu/cpipubs>

 Part of the [Physics Commons](#)

Recommended Citation

Pishnyak, Oleg P.; Nastishin, Yuriy A.; and Lavrentovich, Oleg (2004). Comment on "Self-Organized Periodic Photonic Structure in a Nonchiral Liquid Crystal". *Physical Review Letters* 93(10). doi: 10.1103/PhysRevLett.93.109401 Retrieved from <http://digitalcommons.kent.edu/cpipubs/210>

This Article is brought to you for free and open access by the Department of Chemical Physics at Digital Commons @ Kent State University Libraries. It has been accepted for inclusion in Chemical Physics Publications by an authorized administrator of Digital Commons @ Kent State University Libraries. For more information, please contact earicha1@kent.edu, tk@kent.edu.

Comment on “Self-Organized Periodic Photonic Structure in a Nonchiral Liquid Crystal”

Ruan *et al.* [1] described “a very regular, almost hexagonal, periodic pattern” in a hybrid-aligned (normal orientation of the director \mathbf{n} at one plate and planar at the other) smectic A (SmA) cell and explained it as a lattice of spherical-cylindrical domains (SCDs). We demonstrate that (1) the model does not account for an important energy term caused by discontinuity walls, and (2) the structure is formed by focal conic domains (FCDs) [2] rather than by SCDs.

(1) According to [1], each SCD is composed of a hemispherical domain of radius $a \approx (2-5) \mu\text{m}$ and elastic energy $w_s = 4\pi K a/3$ placed on top of a cylinder with the energy $w_c = (1/3)\pi K(d-a)\ln(a/r_c)$; K is the splay constant, r_c is the defect core radius at the cylinder axis, and d is the cell thickness. The period is deduced from the balance of w_s and w_c [1]. However, the SCD model implies discontinuity walls [such as the plane containing line AB in Fig. 1(a)] with the energy density $\sim K/\lambda$, where $\lambda \approx 3 \text{ nm}$ is the layer spacing in the studied SmA-4-octyl-4'-cyanobiphenyl [2]. The wall energy, not accounted for in [1], $w_{\text{wall}} \sim (K/\lambda)a^2$ is about $a/\lambda \sim 10^3$ times larger than w_s and w_c . Usually the discontinuity walls in SmA relax into defects such as FCDs [2]. The present situation is no exception, as shown below.

(2) We use fluorescence confocal polarizing microscopy (FCPM) that allows one to obtain the vertical optical slices of SmA-4-octyl-4'-cyanobiphenyl samples doped with 0.01 wt. % of dye BTBP [3]. The intensity of light in FCPM texture is maximum when the polarization of light \mathbf{P} is parallel to \mathbf{n} and minimum when $\mathbf{P} \perp \mathbf{n}$ [3]. We use polyimides JALS-204 (JSR Microelectronics) and rubbed PI2555 (Microsystems) for normal and planar alignment, respectively. For $3 \mu\text{m} \leq d \leq 10 \mu\text{m}$, the textures are similar to the “almost hexagonal periodic patterns” of Ref. [1]; the period increases with d . However, FCPM imaging of the vertical XZ planes [Fig. 1(c)], especially for slightly tilted samples [Fig. 1(d)], reveals that the structure is formed by FCDs rather than SCDs. Each FCD has an elliptic base at the planar XY substrate and a hyperbola H in the XZ plane. Dark regions in Fig. 1(c) correspond to $\mathbf{n} \parallel Z$ near the boundary between two FCDs. The tilt [Fig. 1(d)] reveals an additional dark band associated with the hyperbola H . In the SCD model, such a dark part would not occur; on the contrary, the dimmed part would disappear as \mathbf{n} would depart from $\mathbf{n} \parallel Z$ [Fig. 1(b)]. In both FCD and SCD, the layers are perpendicular to the planar plate and experience tilt and splay at the opposite plate.

Contrary to SCDs, the FCD groups do not require drastic discontinuity walls [2,4]; compare lines AB in Fig. 1(a) and line CD in Fig. 1(e). What is new in the present case with the *rubbed* planar substrates is that

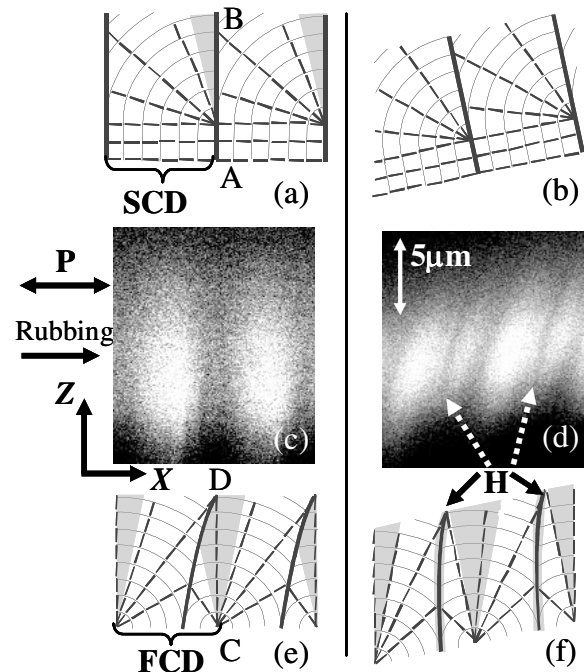


FIG. 1. (a),(b) SCD model of a hybrid-aligned SmA film. (c) FCPM textures of vertical cross section XZ of the SmA sample. (d) the same, tilted by 12° . (e),(f) FCD model that fits the FCPM textures.

many FCDs are of a fragmented type with incomplete ellipses. The missing parts of ellipses correspond to \mathbf{n} orthogonal to the rubbing direction. We relate the fragmentation to azimuthal anchoring caused by rubbing; it is absent at azimuthally degenerate interfaces such as SmA-isotropic fluid. It is well known that the hybrid-aligned SmA at the isotropic substrates shows hexagonal structures formed by FCDs with complete circular bases; see, e.g., [4].

The work was supported by NSF grant DMR-0315523.

O. P. Pishnyak, Yu. A. Nastishin, and O. D. Lavrentovich
Liquid Crystal Institute and Chemical Physics Program,
Kent State University, Kent, Ohio 44242-0001, USA

Received 19 February 2004; published 3 September 2004

DOI: 10.1103/PhysRevLett.93.109401

PACS numbers: 42.79.Dj, 61.30.Jf, 42.70.Qs

- [1] L. Z. Ruan, J. R. Sambles, and I. W. Stewart, *Phys. Rev. Lett.* **91**, 033901 (2003).
- [2] M. Kleman and O. D. Lavrentovich, *Soft Matter Physics: An Introduction* (Springer, New York, 2003).
- [3] I. I. Smalyukh, S. V. Shiyonovskii, and O. D. Lavrentovich, *Chem. Phys. Lett.* **336**, 88 (2001).
- [4] C. Blanc and M. Kleman, *Eur. Phys. J. B* **10**, 53 (1999).